

Trigohexagonite: A Rare Three-dimensional Network of Quaternary Stoichiometry

¹Michael J. Bucknum, ²Bin Wen and ¹Eduardo A. Castro

¹INIFTA, Theoretical Chemistry Division, Suc. 4, C.C. 16,
Universidad de La Plata, 1900 La Plata, Buenos Aires, Argentina

²School of Materials Science and Engineering and
State Key Laboratory of Materials Modification by Laser, Electron and Ion Beams,
Dalian University of Technology, Dalian 116023, China

Abstract: A novel 3-,4-connected network is reported in this communication that is a rare example of a three-dimensional (3D) network with a quaternary stoichiometry, in which 4 distinct sites of bonding occur in the unit pattern of the material. The net lies in the hexagonal space group P-6m2 (#187) and there are 10 vertices (or atoms) in the unit cell, including 4 sites of approximately trigonal planar coordination and 6 sites of approximately tetrahedral coordination. All vertices (atoms) in the network sit on special positions in the P-6m2 space group, giving the network high 6-fold symmetry axes parallel to the crystallographic c-axis. The structure has thus been named trigohexagonite in a loose analogy with its hexagonite crystalline homolog, sitting in the hexagonal space group P6/mmm (#191). The Wells point symbol for the trigohexagonite network is given by $(7^3)(6^3 8^3)_3(6.7^2)_3(3.7^4.8)_3$, where this symbol indicates the quaternary stoichiometry of the network. The Wells point symbol also reveals that the only structural strain present in the network comes from the presence of the 3-gon, cyclopropane-like moieties in it, built on tetrahedral vertices. This structural motif of cyclopropane-like rings has precedent in organic chemistry and it adds character to the overall 6-fold symmetry of the trigohexagonite pattern. Also, the overall network contains rare trimethylenemethane-like clusters of 4 trigonal planar vertices (atoms), bonded together, that constitute the 3-connected component of the network. Both C_{10} and B_{10} realizations are briefly described.

Key words:

INTRODUCTION

A.F. Wells has outlined the basic characteristics of the mathematical-crystallographic problem of the systematic enumeration of the polyhedra, tessellations in 2-dimensions (2D) and crystallographic networks in 3-dimensions, in his important 1977 monograph on the subject [1]. In a later publication in 1984 [2] he reports on the systematic enumeration of about a hundred distinct and novel 3-,4-connected networks of semi-regular Catalan and irregular Wellsean topology and 4-connected networks of semi-regular Archimedean topology. It should be mentioned, in this connection, that more recently, the group led by Delgado-Friedrichs has been applying mathematical algorithms towards the systematic derivation the 3-periodic networks of 3- and 4-

connection [3]. This later group has enumerated 100's of such distinct networks thus far in their continuing project.

Building on the work of Wells in outlining the scope of the problem of the systematic enumeration of networks, Bucknum took the concept of the topology map in a Schläfli space (a space of n and p, the Schläfli symbols for networks) and extended it to include the 3D crystalline networks explicitly [4]. Bucknum showed in 2005 [5] how one could use the topological device that Wells had earlier invented to classify polyhedra, tessellations and networks [1, 2] called the Wells point symbol and translate this notation into an unambiguous and unique Schläfli symbol (n, p) for a structure and thereby map that object in the Schläfli space described above. Such a topology map, in the approximation of the mapping out of the regular or Platonic structures, is indicated in Fig. 1.

n \ P	3	4	5	6	7	8	...
3	t	o	i	(3,6)	(3,7)	(3,8)	
4	c	(4,4)	(4,5)	(4,6)	(4,7)	(4,8)	
5	d	(5,4)	(5,5)	(5,6)	(5,7)	(5,8)	
6	(6,3)	(6,4)	(6,5)	(6,6)	(6,7)	(6,8)	
7	(7,3)	(7,4)	(7,5)	(7,6)	(7,7)	(7,8)	
8	(8,3)	(8,4)	(8,5)	(8,6)	(8,7)	(8,8)	
⋮							

Fig. 1: Topology map of Schläfli space for regular (Platonic) structures

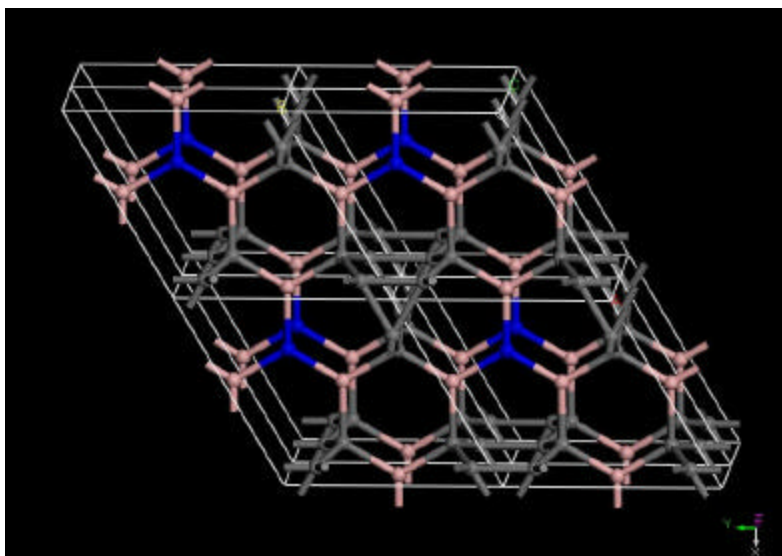


Fig. 2: View of the Wellsean trigohexagonite lattice in space group P-6m2 (#187), from a perspective along the **c**-axis: 3-connected vertices are blue and pink, 4-connected vertices are gray

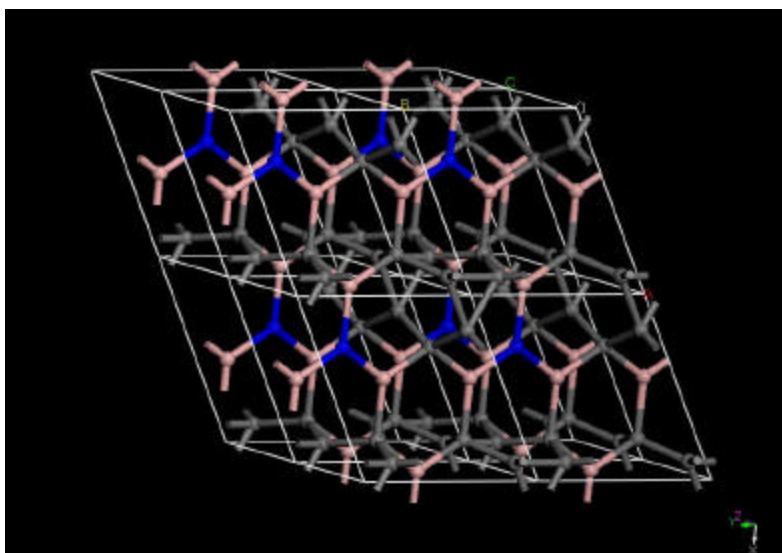


Fig. 3: View of Wellsean trigohexagonite lattice in space group P-6m2 (#187), from the perspective of the **ab**-plane: 3-connected vertices are blue and pink, 4-connected vertices are gray

Table 1: Idealized set of fractional hexagonal crystallographic coordinates of trigohexagonite in the hexagonal space group P-6m2 (#187)

Atom#	x/a	y/b	z/c	a	c
1	1/2	1/2	1/2	5.200Å	2.718Å
2	0	1/2	1/2	"	"
3	1/2	0	1/2	"	"
4	5/6	1/6	1/2	"	"
5	5/6	2/3	1/2	"	"
6	1/3	1/6	1/2	"	"
7	0.90383	0.09617	0	"	"
8	0.90383	0.80767	0	"	"
9	0.19233	0.09617	0	"	"
10	1/3	2/3	1/2	"	"

Trigohexagonite structural-type: In this paper, the authors describe the enumeration of a network in the hexagonal symmetry class, lying in space group P-6m2 (#187), that possesses a rare quaternary stoichiometry of $AB_3C_3D_3$, as is readily revealed by consideration of its Wells point symbol, cited below. Table 1 lists the fractional hexagonal crystallographic coordinates of the 10 atoms within this so-called trigohexagonite unit cell, for a configuration of the hexagonal cell in which the lattice parameters are given as $\mathbf{a} = 5.200 \text{ \AA}$ and $\mathbf{c} = 2.718 \text{ \AA}$. The cell is thus illustrated in Figure 2 and 3, with the hexagonal structure shown, slightly tilted from plane projection, nearly along its crystallographic c-axis, in Figure 2. Figure 3 shows a view of the hexagonal lattice nearly in the crystallographic ab-plane.

From the perspective of the structure shown in Fig. 2, along the \mathbf{c} -axis, one can see that a thematic variation traced in the structure occurs in the form of the 3-ness of its substructures. The triangles seen perpendicular to the \mathbf{c} -axis, represent locally D_{3h} symmetry, cyclopropane-like substructures of the lattice, arranged in a larger triad, about the principal crystallographic 6-fold axis in the unit cell. Similarly, in the unit cell, there is the presence, arranged again in larger triads along the principal 6-fold axis, of the locally D_{3h} symmetry, 1,3,5-trimethylene-cyclohexane-like and trimethylene-methane-like, organic substructures of the lattice. These 3-fold symmetry substructures are thus seen to be stacked along the \mathbf{c} -axis to generate the resulting three-dimensional (3D) network called trigohexagonite, as is evident from the view of the trigohexagonite structure in Fig. 2.

The overall trigohexagonite network, shown in Figure 2 and 3, can thus be seen to have the relatively complex quaternary stoichiometry [2, 5] reflected in the Wells point symbol given by $(7^3)(6^38^3)_5(6.7^2)_5(3.7^4.8)_3$. This Wellsean point symbol [2] can readily be translated into its

corresponding Schläfli symbol of $(n, p) = (6.75, 3.6)$ by the method already outlined by Bucknum *et al.* previously [5]. Finally, there is an alternative scheme for identifying the topology of arbitrary networks with a so-called vertex-symbol notation. This methodology is due to O'Keeffe [6] and will not be pursued further in this communication.

Survey of representative 3-, 4-connected nets and trigohexagonite: One of the earliest 3-,4-connected nets to be described as such, was that of the phenacite structure-type, elucidated by Bragg *et al.* [7]. This was the structure of a silicate mineral (Be_2SiO_4) which possessed a relatively complex, ternary stoichiometry. The structural-type was discovered from analysis of the parent beryllium-containing mineral structure of the formula Be_2SiO_4 . It was an especially challenging structure determination as the unit cell was rhombohedral (R-3) and there were 6 (Be_2SiO_4) formula units within the unit cell.

Bragg *et al.* identified the structural character of the net as follows, "It is difficult to give a clear figure of the structure, because the unit cell is large and a pattern with rhombohedral symmetry is harder to depict than one based upon rectangular axes. The principles of the structure are very simple, however and are readily traced in a model. It is formed of linked tetrahedra, with Si and Be at their centres. Each O of the independent SiO_4 groups also forms part of two neighboring tetrahedra around Be atoms. Thus each Si is surrounded by 4 O atoms and each Be by 4 O atoms and each O is linked to 2 Be atoms and one Si atom at the corners of an equilateral triangle." [7] A general view of this phenacite lattice is taken from Wells [1] and shown in Fig. 4.

The complex ternary stoichiometry of phenacite is reflected in the Wells point symbol for this Wellsean network, as is given by Wells in his A.C.A. monograph on novel networks of 1984 [2] as, $(8^3)_2(6^3)_6(6^38^3)_6$. And this ternary Wells point symbol can therefore be translated into its corresponding Schläfli symbol [5] as $(6^{4/5}, 3.4285\dots)$.

We can thus see by comparison of the topological form indexes [8] of the respective structures, given by the definition $l = n/p$, that compared to the ideal (Platonic) unary, tetrahedral, 4-connected diamond network 6^6 or $(6, 4)$, in which $l = n/p = 1.5$ [1, 8] the phenacite network is a slightly less compact ($l = n/p = 1.9833\dots$) structure-type than diamond is, in its inherent topology. Taking this further, we see that in the quaternary stoichiometry, trigohexagonite network that it is, indeed, intermediate in compactness ($l = n/p = 1.875$) between the most compact,

diamond network and the least compact phenacite network. It should be mentioned in this context, that perhaps the most open such structure that is possible, in terms of the topological form index $l = n/p$ as a measure of "openness" [8] is the Wells constructed series of 3-connected topoisomers identified collectively as 10^3 , or by the translated Schläfli symbol (10, 3) [1] with a form index of $3^{1/3}$.

Bragg *et al.* later report [7] that isostructural 3-,4-connected nets, in a binary A_3B_4 stoichiometry, that is nonetheless patterned as the topologically ternary phenacite structure-type, might be possible for various combinations of Group 14 and 15 elements. From this insight, there were reported the synthesis of Ge_3N_4 by Juza *et al.* [9] in 1939-40 and 17 years later the corresponding silicon-nitride binary compound, Si_3N_4 , was produced by Hardie *et al.* [10] and Ruddleson *et al.* [11] both with work reported in 1957. Therefore the germanium-nitride and silicon-nitride structures, referenced here, were seen to be entirely isostructural with the phenacite structure-type. In the currents of science today, is that elusive corresponding carbon-nitride, β - C_3N_4 , suggested by Cohen *et al.* as a candidate for a superhard material [12] carbon-nitride in the phenacite realization of Cohen *et al.* has, sadly, remained difficult to characterize in various, innumerable synthetic attempts carried out so far around the world [13].

The ternary phenacite structure was evidently the most complex network, in terms of the Wells point symbol, analyzed and published by Wells in his important works on 3-periodic networks of various valences [1, 2]. It is therefore important to point out here in this communication, that the title material described here theoretically, called trigohehexagonite, is perhaps the most complex material yet described, from purely a topological-stoichiometric point of view, as it possesses a quaternary stoichiometry reflected in the Wells point symbol $(7^3)(6^38^3)_3(6.7^2)_3(3.7^4.8)_3$.

In contrast to phenacite and trigohehexagonite described above, a relatively simple topology for a 3-,4-connected net is that found in the so-called Waserite structure-type [14] which represents the anionic Pt_3O_4 sublattice of certain alkali metal platinates of generic chemical formula MPt_3O_4 . The Waserite structural-type is shown in Fig. 5.

It can be seen from Fig. 5 that all circuits in the Waserite structure-type are 8-gons, giving the lattice a classification as Catalan [5]. The Wells point symbol for this lattice is easy to write down as $(8^4)_3(8^3)_4$ as one can readily trace from Fig. 5 [5].

Thus the Catalan nature and the relatively simple binary stoichiometry, of this Waserite network distinguishes it from the otherwise complicated topologies of the phenacite and trigohehexagonite networks described above. The relative orderings of the symmetry space groups of the lattices is also interesting as Waserite lies in the relatively high space group symmetry of $Pm-3n$ (#223), while trigohehexagonite is in space group #187 and phenacite is in space group #166. It is also true that Waserite can assume a configuration of its bonds such that all bond angles are ideal, with the square planar bond angles being 90° and the trigonal planar angles of the 3-connected vertices being held at 120° . This further distinguishes this net as being closer to ideal, compared to the irregular networks of phenacite and trigohehexagonite which cannot adopt ideal bond angles about all vertices in any configuration.

CONCLUSIONS

In this communication, we have described a novel, crystallographic 3-dimensional (3D) network with an unprecedented quaternary stoichiometry, which we have called trigohehexagonite. As revealed in the Wells point symbol for the novel network, given by the stoichiometric formula $(7^3)(6^38^3)_3(6.7^2)_3(3.7^4.8)_3$, there are indeed 4 distinct sites of bonding within the network and it is built upon an admixture of 4 distinct circuits of size 3, 6, 7 and 8. These 4 distinct circuit sizes are combined together with vertices in trigonal, 3-connection and tetrahedral 4-connection to generate the trigohehexagonite lattice. It is not clear from the literature available to us, whether a quaternary network such as this one has ever been enumerated previously.

The relatively simple construction known as the Waserite network, corresponding to the anionic Pt_3O_4 sublattice of the ionic conductor $Na_xPt_3O_4$, provides an interesting counterpoint to the trigohehexagonite structural-type. With the Wells point symbol for Waserite, given as $(8^4)_3(8^3)_4$, we can see that this net is not only of a relatively simple binary stoichiometry (A_3B_4), but that it is also a semi-regular Catalan network in which all circuits in the net are of 8-gon size. It is not clear at this juncture how the onset of topological complexity in a network like trigohehexagonite correlates with the ability to realize such a network in an actual synthesis. Certainly, it would seem that Waserite, which was identified as early as 1951 [14] was synthesized because of the simplicity of its topology, combined with its high degree of symmetry (space group $Pm-3n$, #223). It therefore seems to be the case, that relatively simple topologies combined with high

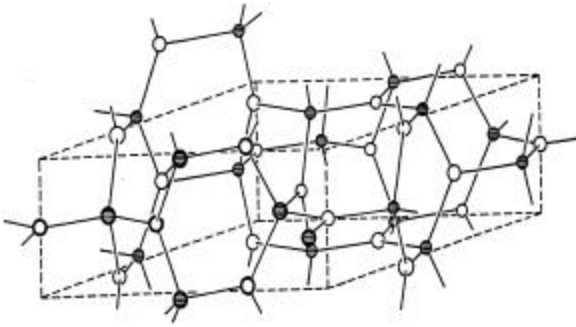


Fig. 4: A view of the crystallographic unit cell of the Wellsean phenacite network in space group R-3m (#166)

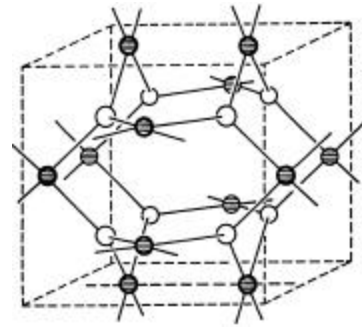


Fig. 5: A view of the Catalan unit cell of Waserite in space group Pm-3n (#223)

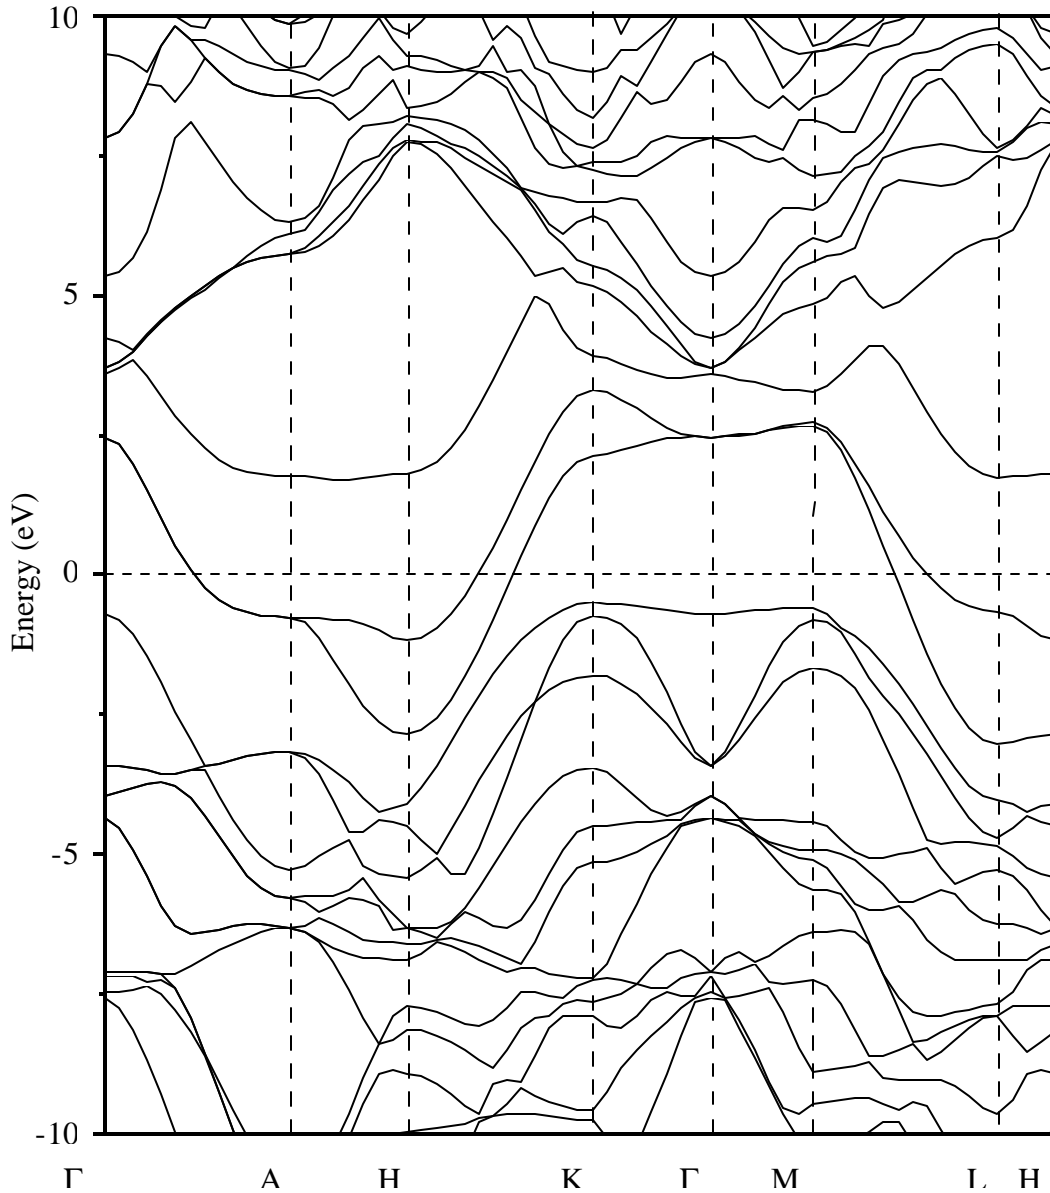


Fig. 6: CASTEP electronic band structure of C₁₀ lattice

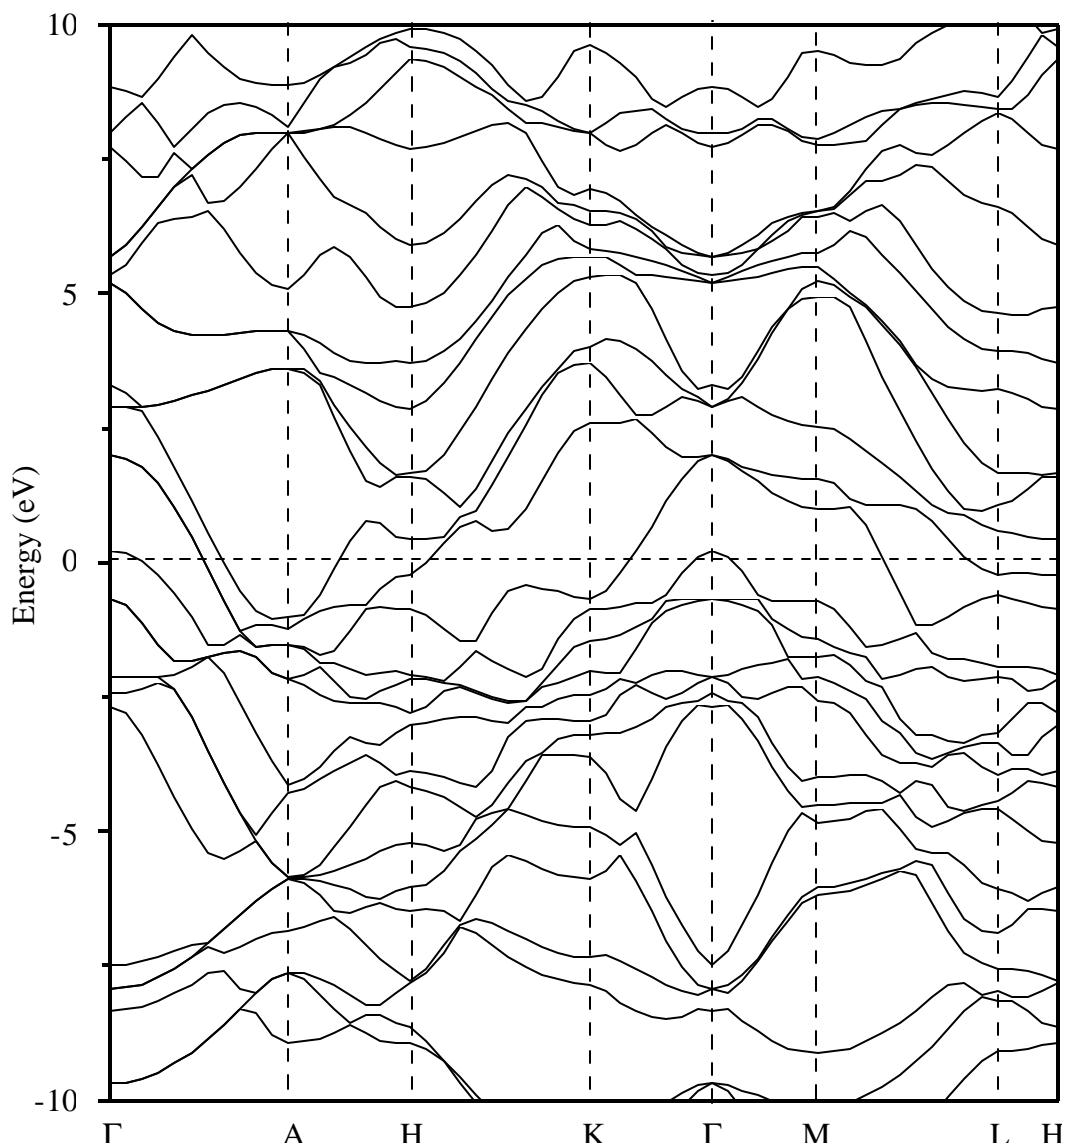


Fig. 7: CASTEP electronic band structure of B₁₀ lattice

Table 2: Set of fractional hexagonal crystallographic coordinates of trigohegonite in the hexagonal space group P-6m2 in a C₁₀ realization

Atom#	x/a	y/b	z/c	a	c
1	0.4970	0.5029	0.5	5.3168Å	2.5628Å
2	0.0059	0.5029	0.5		
3	0.4970	0.9940	0.5		
4	0.8262	0.1738	0.5		
5	0.8262	0.6525	0.5		
6	0.3475	0.1738	0.5		
7	0.9102	0.0898	0.0		
8	0.9102	0.8205	0.0		
9	0.1795	0.0898	0.0		
10	0.3333	0.6667	0.5		

Table 3: Set of fractional hexagonal crystallographic coordinates of trigohegonite in the hexagonal space group P-6m2 in a B₁₀ realization

Atom#	x/a	y/b	z/c	a	c
1	0.4879	0.5120	0.5	5.8183Å	2.9650Å
2	0.0240	0.5120	0.5		
3	0.4879	0.9759	0.5		
4	0.7965	0.2035	0.5		
5	0.7965	0.5929	0.5		
6	0.4071	0.2035	0.5		
7	0.8751	0.1249	0.0		
8	0.8751	0.7501	0.0		
9	0.2499	0.1249	0.0		
10	0.3333	0.6667	0.5		

symmetries are desired characteristics in structures that Nature is able to readily adopt.

This preceding articulated realization, on symmetry and topology and their role in solid state synthesis, can be applied to the allotropes of C for example. The polytypes of diamond are of a Platonic topology given by 6^3 and the graphene grid is Platonic as well, with a Well's point symbol of 6^3 . These archetypal, crystalline structures of C exist, as well, in high symmetry crystallographic space groups [7]. It is also true that diamond, (in its cubic 3C polytype) and graphite, have been known since antiquity. Yet a 3rd family of allotropes of C, the molecular and crystalline fullerenes [15] are collectively semi-regular, Archimedean polyhedra of icosahedral (I_h) and lower degrees of symmetry, that were only discovered synthetically in 1985. The fullerenes collectively possess the Wells point symbol 5^y6^x , where "y" is the number of 5-gons in the respective fullerene polyhedron and "x" is the number of 6-gons in the respective fullerene polyhedron. Collectively, for this infinite family of fullerene polyhedra, the corresponding Schläfli symbol is thus given as $(5^{y/(x+y)}, 3)$ [16]. One can look to the future of C synthesis and see that there have been various proposals for (1) Catalan graphite-diamond hybrid structures, collectively of orthorhombic symmetry, as envisioned by Balaban *et al.* [17] as well as (2) the original proposal of Karfunkel *et al.* [16, 18] of Catalan allotropes of C having potentially high hexagonal symmetry (P6/mmm, #191). And (3) along these lines there are myriad other proposals [19] for C structures including alternative Archimedean, Catalan and Wellsean networks of various high and low symmetries

Finally, with the discussion bearing on a potential realization of the trigohexagonite lattice, we turn to some density functional theory optimizations of potential C_{10} and B_{10} trigohexagonite phases. The density functional theory (DFT) optimization calculations of the geometries of the C and B allotropes, together with a calculation of the electronic structure of each lattice, was carried out using the CASTEP method [20]. The details of this method are reported in [21-24].

In Table 2 and 3 are listed the optimized coordinates of the C_{10} and B_{10} lattices of trigohexagonite, note that the C (or B) atoms don't sit on ideal high symmetry positions, within the hexagonal space group, although the unit cell overall is still in the high symmetry space group of P-6m2 (#187). The lattice parameters of the C trigohexagonite lattice are given as $a = 5.317 \text{ \AA}$ and $c = 2.563 \text{ \AA}$, with a corresponding density of 3.178 g cm^{-3} . The C_{10} realization is moderately dense, but not nearly so dense as cubic

diamond is at 3.56 g cm^{-3} . For the B_{10} realization, the lattice parameters are $a = 5.818 \text{ \AA}$ and $c = 2.965 \text{ \AA}$, with the density being given as 2.065 g cm^{-3} , it is a more open trigohexagonite lattice with B than C, even given the lower atomic weight of B ($10.811 \text{ g mole}^{-1}$) than C ($12.011 \text{ g mole}^{-1}$).

Figure 6 and 7 report the CASTEP calculated electronic band structures of the C and B realizations, respectively. There are 40 bands in each band structure, the bands are generated by symmetry adapted mixing of the occupied s, p_x , p_y and p_z orbitals (through the reciprocal space of the lattice) of the C and B atoms making up the materials. There are thus 20 bonding (σ and π) bands and 20 antibonding bands (σ^* and π^*) in the electronic structure of each material, within a simplified Hückel approximation. The B realization is comprised of 30 valence shell electrons within the unit cell and would be expected nominally to occupy the bottom 15 bands, in energy, in the band structure, while the C lattice with 40 valence shell electrons within the unit cell, would fill the bottom 20 bands in energy.

Both C and B trigohexagonite realizations are electrically conductive phases according to the CASTEP approximation of this complex lattice, as can be seen by the band crossings (much more numerous in the B than the C realizations) of the Fermi levels in the respective lattices. The Fermi level is indicated by the horizontal dashed line in each band diagram. It lies partially between the 20th (a π band) and the 21st (a π^* band) in the C realization, as would be expected for a metallic modification of C. Note also in this C lattice that the π^* bands (the 21st and 22nd bands in this case) dip down into the bonding manifold of the electronic structure to indirectly cross some of the π bands in the structure, at about symmetry points L and H in the Brillouin zone and to create its metallic status. The B realization of trigohexagonite has a considerably more congested structure of bands about its Fermi level, in this case the Fermi energy is expected to be in the vicinity of the 15th band. There are many band crossings in the B structure and the lattice reflects its unique character from C in its very different and congested band profile.

REFERENCES

1. Wells, A.F., 1977. Three Dimensional Nets and Polyhedra. 1st Edn., Wiley and Sons, New York.
2. Wells, A.F., 1979. Further Studies of Three-dimensional Nets, American Crystallographic Association, Monograph #8. 1st Edn., ACA Press.

3. (a) Delgado-Friedrichs, O. *et al.*, 1999. *Nature*, 400: 644-647. (b) Delgado-Friedrichs, O. and M. O'Keeffe, 2003. *Acta Cryst.*, A59: 351-360. (c) Delgado-Friedrichs, O. *et al.*, 2006. *Acta Cryst.*, A62: 350-355.
4. Bucknum, M.J., *Carbon*, 35 (1): 1.
5. Bucknum, M.J. and E.A. Castro, 2005. *Commun. Math Comp. Chem.*, (MATCH), 54: 89.
6. O'Keeffe, M. and B.G. Hyde, 1996. *Crystal Structures I: Patterns and Symmetry*, Mineralogical Society of America. 1st Edn., Mineralogical Society of America Press, Washington, DC.
7. (a) Bragg, W.L. and W.H. Zachariasen, 1930. *Zeits. Fuer Kristoll.*, 72: 518. (b) Bragg, W.L., 1937. *Atomic Structure of Minerals*. Cornell University, 1st Edn., Cornell University Press, Ithaca, NY.
8. Bucknum, M.J. and E.A. Castro, 2006. *J. Math. Chem.*, 40 (4): 327.
9. (a) Juza, R. and H. Hahn, 1939. *Naturwissenschaften*, 27: 32. (b) Juza, R. and H. Hahn, 1944. *Zeits. Anorg. Chem.*, 244: 125.
10. Hardie, D. and K.H. Jack, *Nature*, 180: 332.
11. Ruddleston, S.N. and P. Popper, 1958. *Acta Cryst.*, 11: 465.
12. Liu, A.Y. and M.L. Cohen, 1989. *Science*, 245: 841.
13. Malkow, T., 2001. *Materials Science and Engineering A*, 302 (2): 311.
14. Waser, J. and E.D. McClanahan, 1951. *J. Chem. Phys.*, 19: 413.
15. Kroto, H., J.R. Heath, S.C. O'Brien, R.F. Curl and R.E. Smalley, 1985. *Nature*, 318: 162.
16. Bucknum, M.J. and E.A. Castro, 2006. *J. Chem. Theory and Comp.*, 2 (3): 775.
17. Balaban, A.T., D.J. Klein and C.A. Folden, 1994. *Chem. Phys. Letters*, 217: 266.
18. Karfunkel, H.R. and T. Dressler, 1992. *J. Am. Chem. Soc.*, 114: 2285.
19. Bucknum, M.J., I. Stamatina and E.A. Castro, 2005. *Molecular Physics*, 103 (20): 2707.
20. Payne, M.C. *et al.*, 1992. *Rev. Mod. Phys.*, 64: 1045.
21. In our calculations, lattice parameters of trigohexagonite were optimized by using density functional theory (DFT) and the plane-wave pseudopotential technique implemented in the CASTEP package [22]. The ion-electron interaction was modeled by ultrasoft pseudo potentials [23]. The generalized gradient approximation (GGA) with the PBE exchange-correlation functional.
24. was used. The \mathbf{k} point separation in the Brillouin zone of the reciprocal space was set to be 0.04 nm^{-1} , that is, $5 \times 5 \times 10$ \mathbf{k} points mesh. A high cutoff energy of 800 eV was selected in this work. Within the current computational scheme, the electronic energy band structure and elastic parameters of trigohexagonite were investigated as well.
22. Segall, M.D., P.J.D. Lindan, M.J. Probert, C.J. Pickard, P.J. Hasnip, S.J. Clark and M.C. Payne, 2002. *J. Phys. Condens. Matter*, 14: 2717.
23. Hamann, D.R., M. Schluter and C. Chiang, 1979. *Phys. Rev. Lett.*, 43: 1494.
24. Perdew, J.P., K. Burke and M. Ernzerhof, 1996. *Phys. Rev. Lett.*, 77: 3865.